

Doi: 10.26479/2022.0802.05

Studies on use of yttrium sulphide as the storage electrode in photoelectrochemical (pec) storage cell

U.K. Mohite

Department of Physics, M.B.S.K. Kanya Mahavidyalaya, Kadegaon, Dist.- Sangli-415304(M.S.)

Abstract: The study of yttrium sulphide as storage electrode was carried out by designing a special three electrode storage cell system. It consists of three electrodes, namely, storage electrode, photoelectrode and counter electrode. Electrodeposited yttrium sulphide film and CdSe film on to a stainlesssteel substrate has been used as a storage electrode and photoelectrode respectively. The graphite rod was used as a counterelectrode. These three electrodes were immersed in two rectangular transparent plastic boxes containing suitable electrolytes. Boxes were bridged together by agar-agar gel. The cell was illuminated by a high intensity lamp. The electrical characteristics in the mode of charging and discharging were studied.

Keywords: Storage cell, storage electrode, photoelectrode, counterelectrode and agar-agar gel.


***Corresponding Author:** U.K. Mohite

1. introduction:

Now a day, for a sustainable society, energy is unquestionably one of the grand challenges [1, 2]. In this modern world, the social prosperity and economic development depend on the sustainable energy conversion and storage [2]. Since from 19th century, due to vast consumption of non- renewable fossil fuels resulted in a severe anxiety for energy deficiency and the corresponding carbon emissions, creates new environmental issues. There is urgent need of clean, affordable and reliable energy that can substitute fossil fuels and limits the carbon emission issue. Therefore, the interest of researchers focused towards the development of technology to make availability of clean and renewable energy, especially the intermittent energy, energy conversion and storage [3, 4]. Now a day, there is vast demand for electrochemical energy conversion and storage devices, especially portable devices, consumer electronics, and electric vehicles [5–7]. Derek P Gregory has been reported use of rare earth hydrides for storing hydrogen in both stationary and mobile applications [8]. Therefore, it should require rapid development of new materials with high performance in energy conversion and storage devices. In our opinion, scientists underestimated this field and started working with material having low cost and easy availability. The best materials, for examples,

so far reported with relatively with high efficiency and stability for long time are CdSe, WSe₂, CuIn Se₂[9-12].

Photo electrochemical cell can be converted into rechargeable electrochemical storage cell, when storage electrode, capable of undergoing a reversible chemical change is used in it [13]. A reversible chemical reaction occurs at the storage electrode of the type,



Where A is storage electrode, X is solute present in the electrolyte. Construction of such a cell requires stable low resistance separator which minimizes direct chemical reaction of the electro active redox species, and the selected redox couples suitable to semiconductor photoelectrode. The PEC cells employing third electrode as a storage electrode have been reported in the literature [14-19].

2. Materials and methods:

Preparation of electrode films and electrolytes:

Yttrium-sulphide films have been electrodeposited from the non-aqueous formaldehyde bath [0.05M Y (NO₃)₃ - 0.05M CH₃CSNH₂ - 0.05M CH₃COONa] onto a stainless-steel substrate at room temperature. The CdSe films are electrodeposited from the aqueous bath [0.1M CdCl₂ - 0.05M SeO₂] onto stainless steel substrates. The PEC properties of the film were tested with the electrolyte 0.1 M (Na₂S - S – NaOH) as an electrolyte and graphite as a counterelectrode. In order to increase the photo effect, the films were annealed at 200^oC.

The electrolytes are prepared by using analytical grade chemicals in doubly distilled water. The stable electrolyte for the photoanode (CdSe) is polysulphide [20]. It was prepared by taking A.R. Grade Sodium hydroxide and sulphur from. B.D.H., India, and A. R. Grade sodium sulphide, from the Fluka. Appropriate amount of NaOH and Na₂S were dissolved in double distilled water at room temperature. In this solution, sulphur powder was added and mixture warmed up to 55^oC with constant stirring. The mixture was maintained at this temperature till all sulphur powder dissolves. The solution was cooled to room temperature, filtered and preserved in the glass stopper air tight bottle. The colour of the the solution was yellowish pink. The yttrium sulphide films are stable in the ferri-ferrocyanide electrolyte. This electrolyte was prepared by taking appropriate amount of potassium ferricyanide and potassium ferrocyanide of analytical grade, dissolved in double distilled water and preserved in the glass stopper air tight bottle.

Design of the Three Electrodes Storage Cell:

The design of three electrode battery was reported by many researchers in various journals [21-25]. Here, cell consists of three electrodes, namely, CdSe as a photoelectrode, graphite as counterelectrode and yttrium sulphide as storage electrode. Two rectangular transparent plastic boxes were fixed with M-seal by conducting bridge of 3 cm in length formed with Agar-Agar gel. The size of each rectangular box is 4.0 × 1.5 × 7.5cm³. One compartment of cell consists of CdSe as a photoanode (5cm²area) and graphite rod (6.2cm²area) as the counterelectrode. The volumes of the electrolytes were 35 cc in each compartment of the cell. The electrolyte 0.1 M (Na₂S-NaOH) was used in first compartment. The other compartment consists of 0.1 M [K₃Fe(CN)₆] – K₄Fe(CN)₆] electrolyte with yttrium sulphide storage electrode which is kept in dark.

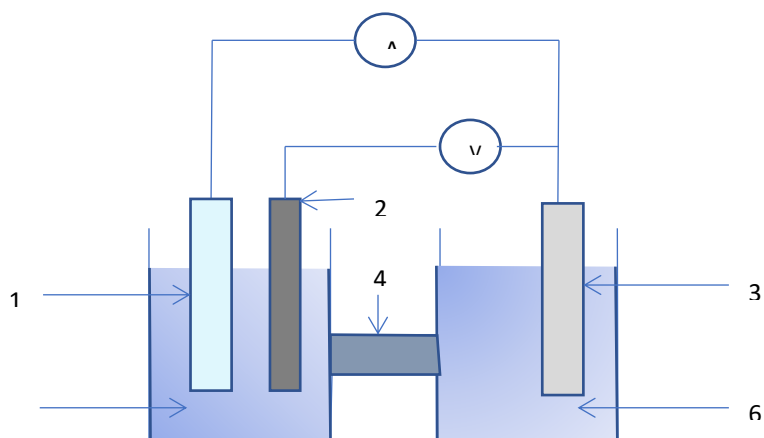


Fig.1: Schematic diagram of the redox storage cell during charging

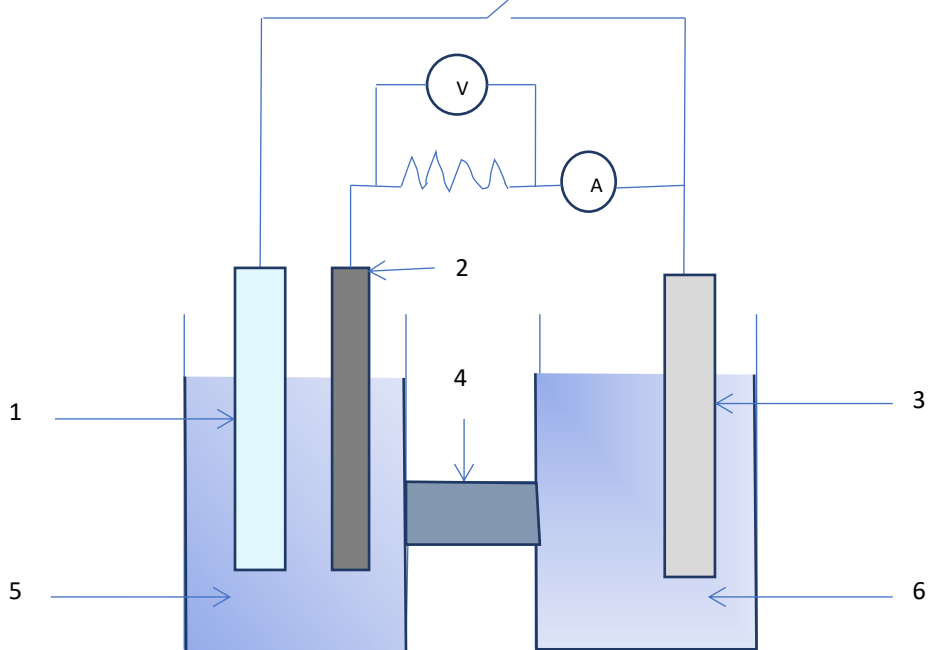


Fig.2: Schematic diagram of the redox storage cell during discharging

The cell was illuminated by using 500-Watt tungsten filament lamp. The light intensity was $200\text{mW}/\text{cm}^3$. The electrical characteristics in the mode of charging were studied with the circuit diagram shown in fig.1 and fig.2 respectively. In fig. 1)- CdSe photoanode, 2)- counter-electrode, 3) Y-S storage electrode, 4) Agar-Agar gel, 5) 0.1 M ($\text{Na}_2\text{S} - \text{S} - \text{NaOH}$) and 6) $\text{K}_3\text{Fe}(\text{CN})_6] - \text{K}_4\text{Fe}(\text{CN})_6$. The current and voltages were recorded using the digital current and volt meters respectively.


3. Result and discussion:

The Configuration of the Cell and Charge Transfer Mechanism:


The configuration of the cell was as follows:

n - CdSe/ 0.1M (Na₂S - S - NaOH) / C / 0.1M - [K₃Fe(CN)₆] - K₄Fe(CN)₆] / Y - S.


During charging the photoreaction occurring at the two electrodes can be described as follows:



Due to localized electric field at junction,




(i.e. near the interface of the semiconductor electrolyte)



i.e. oxidation of electrolyte would occur, which is present near interface.




(Transfer to through back of semiconductor to the storage electrode)



when Y-S was the storage electrode.

Charging and Discharging Studies of the CdSe/ 0.1M (Na₂S - S - NaOH) / C / 0.1M - [K₃Fe(CN)₆] - K₄Fe(CN)₆] / Y - S.

During the period of charging, photocurrent raised from 0.15 to 0.225 mA/cm², while cell voltage rose from 30 to 200 mV as shown in fig.3 within the period of 120 minutes.

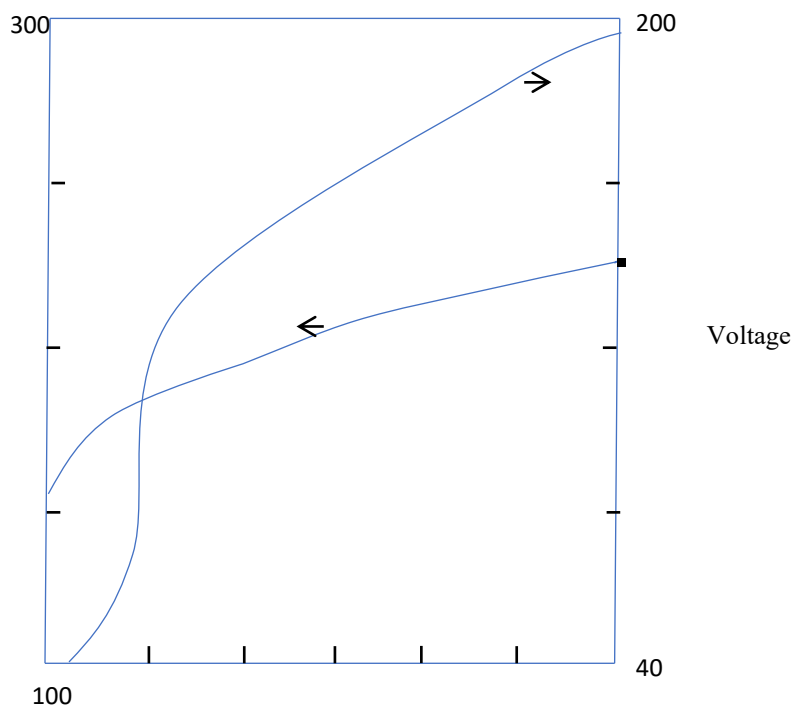

Discharging of the cell using $6\text{ K}\Omega$ load across the storage electrode and counterelectrode results in an initial current of $25\ \mu\text{A}/\text{cm}^2$ and after the period of two hours current drops to $6\ \mu\text{A}/\text{cm}^2$. The cell voltage also decreased from 600 to 300mV as shown in fig.4. It can be seen that the potential drops rather severely under load. This is attributed to resistance losses in the systems such as those in the photoactive layer and electrolyte, polarization losses at the counterelectrode and semiconductor metal contact.

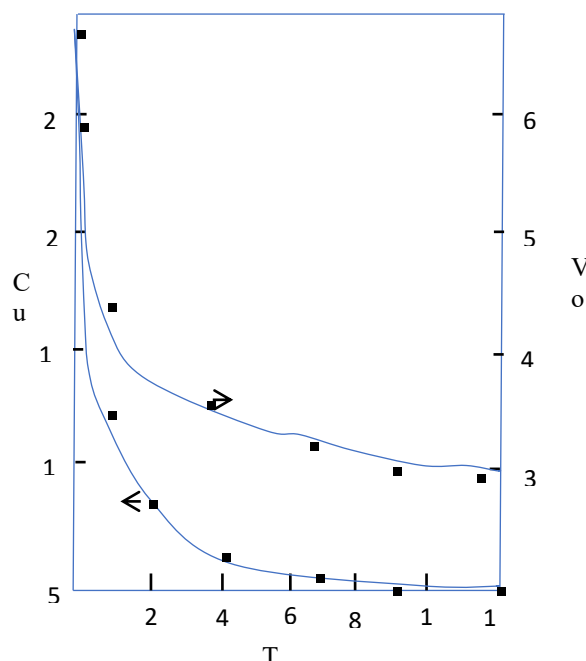


Fig.4: Discharging

4. Conclusion:

From above studies of charging and discharging characteristics, it is concluded that yttrium sulphide film may be used as a storage electrode.

Acknowledgement:

The author thankful to Principal Dr. V. Y. Kadam, M.B.S.K. Kanya Mahavidyalaya, Kadegaon, for encouragement and provision of necessary facilities. The author is thankful to Dr. C. D. Lokhande, former Professor and Head of the Physics Department of Shivaji University, Kolhapur. Also, author is thankful to and all departmental faculties for kindly sharing their knowledge with me, for their suggestions and fruitful discussions.

References:

- [1] Arico AS, Bruce P, Scrosati B, Tarascon J M, Van Schalkwijk W, Nanostructured materials for advanced energy conversion and storage devices, *Nat. Mater.* 2005;4: 366–367.
- [2] Chu S, Majumdar A, Opportunities and challenges for a sustainable energy future, *Nature*, 2012;488:294–303.
- [3] Liu C, Li F, Ma LP, Cheng HM, Advanced Materials for Energy Storage, *Adv. Mater.* 2010;22: 28–62.
- [4] Manthiram A, Fu Y, Chung SH, Zu C, Su YS, Rechargeable Lithium–Sulfur Batteries *Chem. Rev.* 2014; 114: 11751–11787.

- [5] Lv W, Li Z, Deng Y, Yang QH, Kang F, Graphene-based materials for electrochemical energy storage devices: Opportunities and challenges, *Energy Storage Mater.* 2016;2: 107–138.
- [6] Yu-Guo Guo, Jin-Song Hu, and Li-Jun Wan, Nanostructured Materials for Electrochemical Energy Conversion and Storage Devices, *Adv. Mater.* 2008; 20: 2878–2887.
- [7] Luhan Ye, Kechun Wen, Zuoxiang Zhang, Fei Yang, Yachun Liang, Weiqiang Lv and et. al., Highly Efficient Materials Assembly Via Electrophoretic Deposition for Electrochemical Energy Conversion and Storage Devices, *Advanced Energy Materials.* 2016: Review.
- [8] Gregory Derek P, Prospects for the use of hydrogen as an energy carrier; *Proceedings of the 13th Rare earth conference held at Whelung, West Virginia.* 1977; 1:16-19.
- [9] J. Manassen, G. Hodes and D. Cahen, Semiconductor liquid junction solar cells, *Electrochemical soc.* 1977: 77:34-38.
- [10] Xiaohui Zhang, Bin Yao, Yongfeng Li, Zhanhui Ding, Haifeng Zhao, Ligong Zhang and et. al. Influence of WSe₂ buffer layer at back electrode on performance of Cu₂ZnSn (S,Se)₄ solar cells, *Solar Energy.* 2020;199:128-135.
- [11] Gutierrez MT and Ortega J, Photoelectrochemical Study of Electrodeposited Polycrystalline CdSe in Ferro-Ferricyanide System, *J. Electrochem. Soc.* 1989; 136:2316-2320.
- [12] Ueno Y, Kaigawa H, Ohashi T, Sugiura T and Minoura H, Chemical bath precipitation of CdSe particles for use in a photoelectrochemical cell, *Solar Energy Mat.* 1987;15:421-430.
- [13] Sharon Maheshwar, Veluchamy P, Natarajan C, Kumar Dhananjay, Solar rechargeable battery—principle and materials, *Electrochimica Acta.* 1991;36:1107-1126.
- [14] Joost Manassen, Gary Hodes and David Cahen, Photoelectrochemical Energy Conversion and Storage: The Polycrystalline CdSe Cell with Different Storage Modes, *Journal of Electrochemical Soc.* 1977;124:532-534.
- [15] Liuyue Cao, Maria Skyllas-Kazacos, and Da-Wei Wang, Solar Redox Flow Batteries: Mechanism, Design, and Measurement, *Advance Sustainable Systems; Review.* 2018:1-33.
- [16] Gadave KM, Bhosale CH and Lokhande CD, Electrochemical storage cell formed with HgS films, *Bull. of electrochem.*, 1993;9:262-263.
- [17] Lokhande CD, Uplane MD and Pawar SH, Studies on photoelectrochemical storage cells formed with CdS: Cu electrode, *Solid State Communication.* 1982;43:623-626.
- [18] Dhumure SS and Lokhande CD, Studies on photoelectrochemical storage cells formed with chemically deposited CdSe and Ag₂S electrodes, *Sol. Energy Matter. and Sol. Cells.* 1993;29:183-194.
- [19] Pawar SH, Patil MP and Shinde VN, Photoelectrochemical redox storage cell using electrodeposited CdSe as semiconductor-septum *Bull. of Electrochem.*, 1993;9:252-254.
- [20] Dhumure SS and Lokhande CD, Studies on photoelectrochemical storage cells formed with chemically deposited CdSe and Ag₂S electrodes, *Solar Energy Materials and Solar Cells.* 1993; 29:183-194.
- [21] Costard J, Ender M, Weiss and Ivers-Tiffée E, Three-Electrode Setups for Lithium-Ion Batteries. *Journal of the Electrochemical Society.* 2017;164(2):80-87.
- [22] Song JY, Lee HH, Wang YY and Wan CC, Two and Three-Electrode Impedance Spectroscopy of Lithium Ion Batteries, *Journal of Power Sources.* 2002;111: 255-267.
- [23] Robert D. Minter, Daniel J. Robles, Conner Fear, Yevgen Barsukov and Partha P. Mukherjee, Three-electrode Coin Cell Preparation and Electrodeposition Analytics for Lithium-ion Batteries, *Journal of visualized Experiments.* 2018; 135:57735.
- [24] Goodenough JB and Park KS, The Li-Ion Rechargeable Battery: A Perspective, *Journal of American Chemical Society.* 2013; 135 (4): 1167-1176.

[25] Johannes Landesfeind, Daniel Pritzl, and Hubert A. Gasteiger, An Analysis Protocol for Three-Electrode Li-Ion Battery Impedance Spectra, 2017; 164:1773-1783.